

General product description

For components in general mechanical engineering and automotive engineering that are nitrided due to high wear, such as gears, connecting rods or shafts. Nitriding steel 31CrMoV9 is used when components are exposed to high surface stress and dynamic loads. Depending on the nitriding temperature, surface hardness values of 650 - 800 HV 0.5 can be achieved through gas nitriding.

Individual bar hardening - homogeneity makes the difference

Compared to conventionally hardened products, the microstructure, strength, toughness, straightness, and residual stress state are significantly improved after individual bar hardening. Additionally, this process works with low decarburization and scale formation and drastically reduces hardness distortions. The dimension range for individual bar hardening is Ø 15-80 mm.

International designation

Steel number	EU/DE	ASTM	JIS	AFNOR	B.S.	SIS
1.8519	31CrMoV9	-	-	-	-	-

Chemical composition (cast analysis in percentage by mass)

Element	C	Si	Mn	P	S*	Cr	Mo	V
min.	0,27	-	0,40	-	-	2,30	0,15	0,10
max.	0,34	0,40	0,70	0,025	0,035	2,70	0,25	0,20

Deviation of the piece analysis from the melt analysis according to ISO EN 683-5 : 2017 Table 3.
Customer-specific analyses are possible upon request. For example, steel grade X can be supplied with a lower sulfur content.

Mechanical-technological properties

Characteristic d [mm]	R _{p0,2} [N/mm ²]	R _m [N/mm ²]	A ₅ [%]	Z [%]	KV _{RT} [J]
16 < d ≤ 40	900	1100 – 1300	9	35	25
40 < d ≤ 80	800	1000 – 1200	10	40	30

According to ISO EN 683-5: 2017, customer-specific mechanical properties and other dimensions are possible upon request.

Dynamic properties

31CrMoV9 +HH +QT +SH	Bending fatigue strength σ_{bw} [MPa]	Tensile strength R_m [MPa]
Formel: $\sigma_{bw} \sim 0,5 R_m$	~ 500	~ 1100

Calculated

Physical properties

properties	approx. value
Density in kg/dm^3	7,73
E-module in GPa	210
Electrical resistance at 20 °C in $\Omega \text{ mm}^2/\text{m}$	0,19
Thermal conductivity at 20 °C in $\text{W} / (\text{m K})$	43
Specific heat capacity at 20 °C in $\text{J} / (\text{kg K})$	441

Microstructure

The microscopic oxide purity grade according to DIN 50602 can be agreed. The grain size according to ASTM E 112 is > 5 .

Surface finish

The surface finish complies with the specifications of EN 10277. Ultrasonic full volume testing is possible. In the standard version, the rod ends up to 50 mm are untested.

Condition of delivery


Bright steel, quenched and tempered, peeled.

Miscellaneous

Other agreements according to order

Hardenability

31 CrMoV9

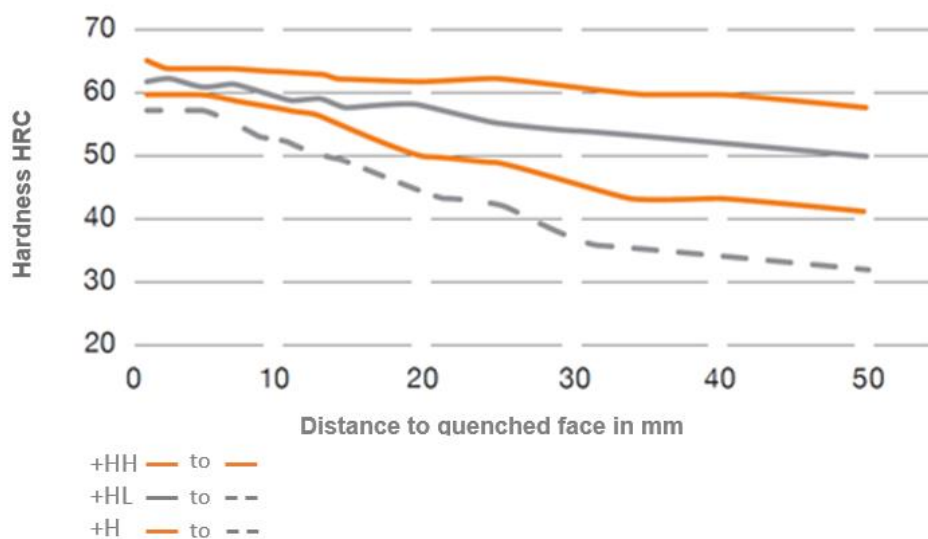

Without further specification we use the quality +HH.

For further info on our product range of tool steel, stainless steel and Engineering steel please visit www.swisssteelgroup.com

30.06.23 Rev. N°1

Discover our Green Steel portfolio on www.swissgreensteel.com

The information and data contained in this document represent standard or average values and do not constitute a warranty or guarantee of minimum or maximum values. The information contained in our material test certificates is solely authoritative. Application recommendations for the materials described in this document are provided for guidance only to enable the reader to make their own decisions and do not constitute an express or implied warranty or guarantee that a material is suitable for a particular application.

Subject to change, errors and printing mistakes. The desired performance characteristics are only binding if they are exclusively agreed upon at the time of contract conclusion.

Swiss Steel Group
 Steeltec AG / Steeltec GmbH:
 Emmenbrücke / Düsseldorf / Gebze
info.engineering@swisssteelgroup.com